

## MWCNTs synthesis from butanol, diethyl ether, ethyl acetate and hexane by chemical vapor deposition with a stainless steel core as catalyst

Granados-Martínez F.G. \*, Contreras-Navarrete J. J., García-Ruiz D. L., Gutiérrez-García C.J., Durán-Navarro A., Gama-Ortega E.E., Flores-Ramírez N., Domratheva-Lvova L.

*Universidad Michoacana de San Nicolás de Hidalgo*

*Gral. Francisco J. Múgica S/N, Felicitas del Río, 58030, Morelia, Michoacán, México.*

García-González L., Zamora-Peredo L.

*Centro de Investigaciones en Micro y Nanotecnología, Universidad Veracruzana  
Calzada Ruiz Cortines, 455, Costa Verde, 94294, Boca del Río, Veracruz, México.*

Mondragón-Sánchez M. L.

*Instituto Tecnológico de Morelia*

*Av. Tecnológico 1500. Lomas de Santiaguito 58120, Morelia, Michoacán, México*

(Recibido: 5 de Julio de 2015; Aceptado: 13 de Noviembre de 2015)

A stainless steel core catalyst with several green precursors, butanol, diethyl ether, ethyl acetate and hexane, were used to obtain multi-walled carbon nanotubes via chemical vapor deposition. Argon was used as carrier gas at 50-90 ml/min rates. Samples were synthesized at 680-850 °C, according to the precursor used. The characterization techniques were scanning electronic microscopy, X-ray diffraction, energy dispersive, Fourier transformed infrared and Raman spectroscopy. The micrographs showed tangled carbon nanotubes formation with different diameters from 50-300 nm. Elemental analysis indicated carbon atomic percentages ranging from 93-99 %, 1.0-4.5 % iron and less than 1% of manganese, chrome and silicon. X-Ray diffraction demonstrated the characteristic carbon nanotubes peak (002) at 26°. G and D carbon nanotubes distinctive bands were confirmed by Raman spectra for all samples.

**Keywords:** multi-walled carbon nanotubes; chemical vapor deposition; synthesis

### 1. Introduction

Green Nanotechnology encourages a vision of collaboration and development that uses scientific research to fundamentally move towards sustainability. In terms of design processes with less energy and resource expense, green methods applied to nanotechnology involve the improvement of performances and the use of materials without adverse consequences to human and environment [1].

The unique chemical and physical properties of Carbon Nanotubes (CNTs) have promoted an extensive research on nanostructural materials. There are several methods that have been used to produce CNTs. Chemical Vapor Deposition (CVD), which is one of the commonly used methods, offers low cost and flexibility [2]. The method is practical due to process parameters control, and the ease to scale up the synthesis process [3]. It has been reported that using the CVD method, organic precursors and metal catalysts, generate a good yield of CNTs with fewer defects [4-10]. The high cost of commonly used precursors have confined CNTs synthesis to research laboratories; therefore, the importance in searching for new natural renewable carbon sources that have low cost and are easy to obtain [11].

The emerging field of nanoscience applies green chemistry and green engineering principles to the synthesis of nanomaterials by achieving an understanding between nanotechnology, innovation and green chemistry [12, 13].

The analysis of traditional carbon nanotubes synthesis is encouraged to reduce environmental and health sideeffects, incorporating alternative carbon sources in future methodologies designs. The present paper outlines an exploration on environmental friendly renewable precursors.

The purpose of this research was the synthesis of Multi-Walled Carbon Nanotubes (MWCNTs) throughout a sustainable process from butanol, diethyl ether, ethyl acetate and hexane by chemical vapor deposition with a stainless steel core as catalyst.

### 2. Experimental procedure

#### 2.1 Materials and methods

CNTs were produced from butanol, diethyl ether, ethyl acetate and hexane with a stainless steel AISI 304 catalyst tube. A quartz tube of 0.0254 m diameter and 0.6 m length was used as reactor. The reactor was heated by an electric tubular furnace. Argon was used as carrier gas and to maintain an inert atmosphere during process. Precursors were loaded into the reactor. The temperatures process was 800 – 850 °C for butanol and hexane, 680 °C for diethyl ether, and 800 – 815 °C for ethyl acetate. Process was performed at atmospheric pressure. Carbon nanotubes growth required carbon source pyrolysis. CNTs time synthesis was between 30 to 40 min. The reactor cooled

\* grana2francisco@gmail.com

**Table I.** CNTs diameters obtained from carbon precursors

Precursor	CNTs diameters (nm)
Butanol	55-230
Diethyl ether	80-200
Ethyl acetate	100-250
Hexane	123-136

down at room temperature once the reaction was concluded. The nanotubes found on the catalyst surface were collected to further analysis.

## 2.2 Characterization techniques


CNTs morphology was analyzed by Scanning Electron Microscopy (SEM) with JEOL JSM-5910LV attached with an Energy Dispersive Spectroscopy (EDS) equipment in order to obtain element percentages. CNTs infrared spectra were registered through a Fourier Transformed Infrared (FTIR) Tensor 27 Bruker. CNTs average microstructure was studied from diagrams obtained by X-ray powder diffraction (XRD) in a Bruker D8 Advance diffractometer (Cu K $\alpha$  = 0.1506 nm,  $20 \leq 2\theta \leq 80$  with 0.0355°/s). MicroRaman DXR Thermo Scientific (solid state laser 532 nm) was used for Raman spectroscopy.

## 3. Results obtained

CNTs synthesized were depicted along SEM and EDS, both analysis provide a clear picture on the growth, overall structure and elemental composition of the nanostructures. These techniques confirmed the presence of MWCNTs with some structural defects. Nanotubes diameters are summarized in Table 1.

Figure 1(a) shows CNTs from butanol with different shape and similar size. Samples contain carbon (99.16 %) and iron (0.84 %).

SEM micrograph of CNTs obtained through diethyl ether is shown on Figure 1(b) with some nanoparticles attached to the nanotubes. EDS depicted carbon around 93% with a

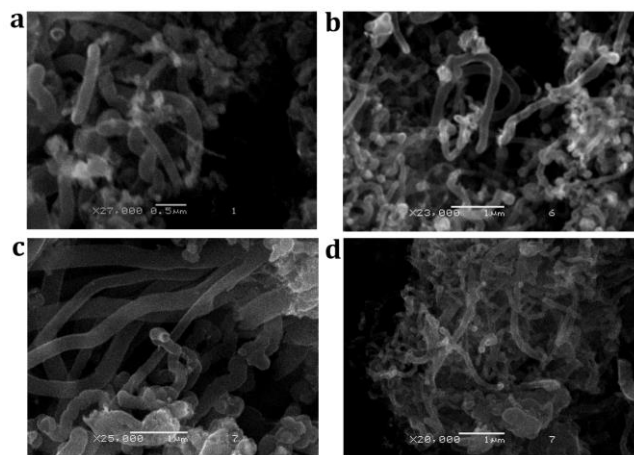

**Figure 1.** SEM micrographs of CNTs obtained from: (a) butanol, (b) diethyl ether, (c) ethyl acetate and (d) hexane.

small presence of oxygen 5% and smaller percentages of iron, chrome and manganese.

The analysis of CNTs morphology synthesized with ethyl acetate (Figure 1(c)) indicated random growth. Carbon (94.77 %), oxygen (4.45 %) and iron (1.53 %) were found by energy dispersed spectroscopy.


Bulks of CNTs from hexane are observed in Figure 1(d). EDS was used to determine atomic percentages and results were 94.77 % of carbon, 4.35 % of oxygen, 0.57 % of iron and 0.35 % of chrome.

MWCNTs FTIR spectra are shown in Figure 2. The region around 3040 to 2840  $\text{cm}^{-1}$  corresponds to  $\text{CH}_x$  vibrations. The 3040  $\text{cm}^{-1}$  signal fits in the stretch for  $\text{sp}^2$ -CH characteristic of aromatic rings [14]. The signals from 2997 and 2886  $\text{cm}^{-1}$  can be attributed to stretching vibration of  $\text{CH}_2$  and  $\text{CH}_3$  [15]; these vibrations are commonly found in multi-walled carbon nanotubes obtained by CVD [16]. The intensity at 1650  $\text{cm}^{-1}$  is associated to C=O stretching of a conjugated ketone [15].


The carbon stretching skeleton vibrations for most carbon materials can be found in the range 1582-1400  $\text{cm}^{-1}$ , like the E1u from the  $\text{sp}^2$  hybridized carbon at 1570  $\text{cm}^{-1}$  [15, 17]. The CNTs obtained from the four precursors showed similar signals and intensity peaks in FTIR spectra, however the intensities of carbon nanotubes from butanol and hexane were better defined.

XRD was used for CNTs phase identification Figure 3. Spectra analysis showed a reflection peak centered at  $2\theta \approx 23^\circ$  related to graphene sheets loosely stacked, different from the crystalline graphite [18]. The located peak in samples with all precursors at  $2\theta \approx 26^\circ$  is characteristic to the reflection of hexagonal graphite (002) reported for carbon nanotubes [19, 20]. Figure 3(a) shows a peak at  $2\theta = 43^\circ$  that correspond to (100) diffraction for CNTs [21].

Raman spectroscopy was used to identify CNTs structures and defects that appear in the sample. The typical band for CNTs, called G band [22], was found at 1572, 1570, 1568 and 1589  $\text{cm}^{-1}$  from CNTs produced with butanol, diethyl ether, ethyl acetate and hexane respectively in Figure 4. D band is assigned to defects in CNTs [23]. CNTs from hexane show a large width D band, similar to Shiratori

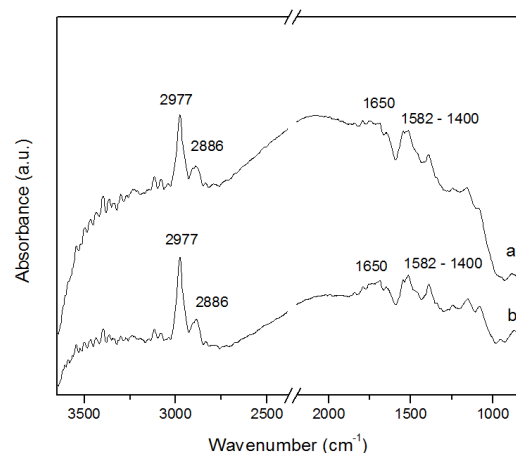

**Figure 2.** CNTs FTIR spectra from: (a) butanol and (b) hexane.

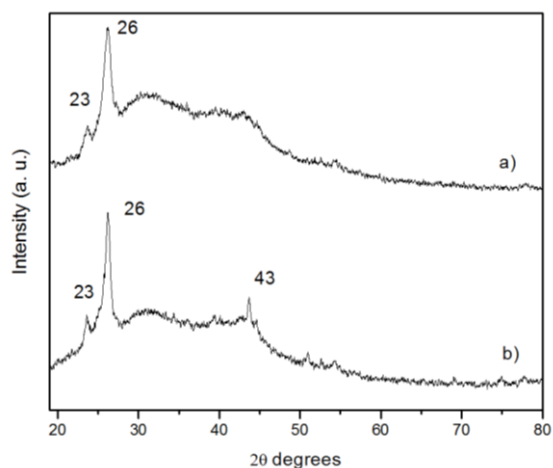


**Figure 3.** X-Ray diffraction analysis of CNTs from: (a) hexane and (b) ethyl acetate.

et al. signal, indicating that the sample contains crystal defects and bond distortions in the CNTs [22]. Antunes et al., suggested that the ratio  $I_D/I_G$  is sensitive to structural defects but not diameter variation, also the line width of D band can be a parameter related to account overall defect density [23]; hence, the nanotubes produced by butanol and ethyl acetate contain similar imperfections ( $I_D/I_G = 1.4$ ). A higher intensity of D band in these CNTs might be for the twister formation. The RBM Raman feature is usually weak to be observable in MWCNTs and the ensemble average of inner tubes diameter broadens the signal [24]. CNTs samples from all precursors show a significant broad with maximum intensities at 282 and 277  $\text{cm}^{-1}$ .

#### 4. Conclusions

Multiwalled carbon nanotubes were synthesized by chemical vapor deposition from butanol, diethyl ether, ethyl acetate and hexane by chemical vapor deposition with a stainless steel core as catalyst. The presence of CNTs with minimum secondary products was confirmed, through SEM, EDS, FTIR, XRD and Raman. The experimental conditions,

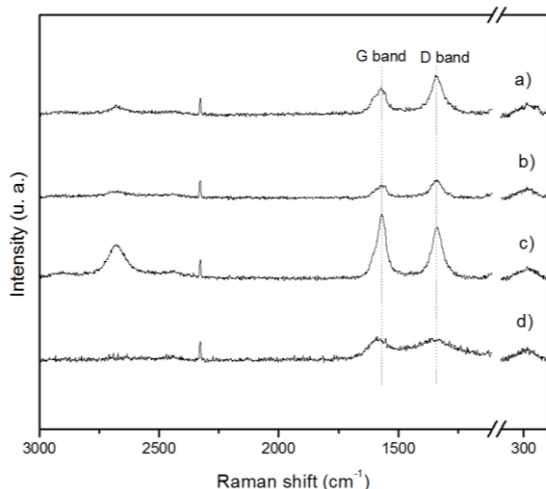

**Figure 4.** CNTs Raman spectroscopy from: (a) butanol, (b) diethyl ether, (c) ethyl acetate and (d) hexane.

organic precursor and catalyst used in this research provide an alternative to synthesized carbon nanotubes reducing the environmental impact due to their low toxicity and relatively easy handling features.

#### Acknowledgments

Acknowledgments to Coordinación de Investigación Científica projects of Universidad Michoacana de San Nicolas de Hidalgo and to Collaboration Network “Nanostructured Materials” of PRODEP (SEP, Mexico).

#### References

- [1]. P. Anastas, J. Zimmerman, *Environ. Sci. Technol.* **37**, 94A (2003).
- [2]. M. Kumar, Y. Ando, *J. Nanosci. Nanotech.* **10**, 3739 (2010)
- [3]. E. Van Hooijdonk, C. Bittencourt, R. Snyders, J. F. Colomer, *Beilstein J. Nanotechnol.* **4**, 129 (2013).
- [4]. Y. Murakami, Y. Miyauchi, S. Chiashi, S. Maruyama, *Chem. Phys. Lett.* **374**, 53 (2003).
- [5]. A. Grüneis, M. Rümeli, C. Kramberger, A. Barreiro, T. Pichler, R. Pfeiffer, H. Kuzmany, T. Gemming, B. Büchner, *Carbon* **44**, 3177 (2006).
- [6]. A. M. Cassell, J. A. Raymakers, J. Kong, H. Dai, *J. Phys. Chem. B* **103**, 6484 (1999).
- [7]. S. Maruyama, R. Kojima, Y. Miyauchi, S. Chiashi, M. Kohno, *Chem. Phys. Lett.* **360**, 229 (2002).
- [8]. H. Qi, C. Qian, J. Liu, *Chem. Mater.* **18**, 5691 (2006).
- [9]. H. E. Unalan, M. Chhowalla, *Nanotechnology* **16**, 2153 (2005).
- [10]. A. Gómez, P. González, L. García, F. Granados, N. Flores, V. López and L. Domratheva, *J. Anal. Appl. Pyrol.* **113**, 483 (2015).
- [11]. S. Paul, S. Samdarshi, *New Carbon Mater.* **26**, 85 (2011).
- [12]. P. Anastas, N. Eghbali, *Chem. Soc. Rev.* **39**, 301 (2010).
- [13]. B. Karn, S. S. Wong, *Sustainable nanotechnology and the environment: advances and achievements* **1124**, American Chemical Society **1124**, 1 (2013).
- [14]. D. Pavia, G. Lampman, G. Kriz, J. Vyvyan, *Introduction to spectroscopy: cengage learning*, ed. Cole, 4th E, 2008
- [15]. L. H. Teng, *J. Zhejiang Univ-Sc A* **9**, 720 (2008).
- [16]. Y. S. Jung, D. Y. Jeon, *Appl. Surf. Sci.* **193**, 129 (2002).
- [17]. N. Kouklin, M. Tzolov, D. Straus, A. Yin, J. Xu, *Appl. Phys. Lett.* **85**, 4463 (2004).
- [18]. Y. Luo, D. Kong, Y. Jia, J. Luo, Y. Lu, D. Zhang, Q. Kangwen, L. Chang, Y. Ting, *Rsc Advance* **3**, 5851-5860.
- [19]. G. Allaedini, P. Aminayi, S. M. Tasirin, *J. Nanomater.* **501**, 961231 (2015).
- [20]. P. Mahanandia, P. Vishwakarma, K. Nanda, V. Prasad, K. Barai, A. Mondal, S. Sarangi, G. K. Dey, S.V. Subramanyam, *Solid State Commun.* **145**, 143 (2008).
- [21]. A. Cao, C. Xu, J. Liang, D. Wu, B. Wei, *Chem Phys. Lett.* **344**, 13 (2001).
- [22]. Y. Shiratori, H. Hiraoka, M. Yamamoto, *Mater. Chem. Phys.* **87**, 31 (2004).
- [23]. E. Antunes, A. Lobo, E. Corat, V. Trava-Airoldi, *Carbon* **45**, 913 (2007).
- [24]. M. S. Dresselhaus, G. Dresselhaus, R. Saito, A. Jorio, *Phys. Rep.* **409**, 47 (2005).