

# A facile method to prepare hexagonal molybdenum trioxide microrods

Vargas-Consuelos C. I.

Facultad de Ciencias, Universidad Autónoma del Estado de México, Campus El Cerrillo  
Piedras Blancas, Carretera Toluca – Ixtlahuaca, Kilómetro 15.5, Edo. de México

Camacho-López M.\*

Laboratorio de Investigación y Desarrollo de Materiales Avanzados, Facultad de Química  
Universidad Autónoma del Estado de México  
Campus Rosedal, Km 14.5, Carretera Toluca-Atacomulco, San Cayetano de Morelos C.P. 50925  
(Recibido: 20 de abril de 2014; Aceptado: 28 de noviembre de 2014)

We report the successfully preparation of straight and well faceted hexagonal-MoO<sub>3</sub> rods by a simple method consisting of a thermal treatment at low temperature applied to molybdenum diluted in a mixture of HCl and HNO<sub>3</sub>. We have obtained sub-micrometer hexagonal rods several microns long with defect free walls. Electron scanning microscopy (SEM) and microRaman spectroscopy were used to characterize the obtained rods. Our results demonstrate the feasibility of synthesizing h-MoO<sub>3</sub> in a very simple way.

**Keywords:** Hexagonal-MoO<sub>3</sub>; MicroRaman spectroscopy; Microrods

## 1. Introduction

Hexagonal molybdenum trioxide (h-MoO<sub>3</sub>) is an attractive material by its peculiar morphology when it is obtained as well faceted rods. This specific feature can be an advantage in terms of applications. J. Song et al. have studied the electrochemical properties of intercalation of lithium into the hexagonal phase of MoO<sub>3</sub>, showing that this material has potential application for secondary lithium ion batteries [1,2]. According to another work by J. Song et al. the hexagonal phase presents photoluminescent properties with emission bands at 436, 606 and 668 nm when the excitation is at 330 nm [3].

Various synthesis methods have been reported to obtain h-MoO<sub>3</sub> [1-13]. Almost all the methods to obtain h-MoO<sub>3</sub> are based in hydrothermal treatments. S. Deki et al. have reported the h-MoO<sub>3</sub> synthesis by liquid phase deposition. They showed that the diameter and length of the hexagonal rods can be modified changing the reaction time [12]. For a 36 h of reaction time, they obtained rods with a diameter and length of 16 μm and 30 μm, respectively. Depending on the synthesis method, the hexagonal rods are defect free on the surface walls. A. Chithambararaj et al. report the effect of temperature of synthesis on the crystal structure of molybdenum trioxide using a hydrothermal method [13]. Characterization studies of the hexagonal phase have been reported in the literature. X-Ray diffractograms, Fourier transform infrared spectra (FTIR), Raman spectra [5-9] are

known and present features clearly different compared to the other polymorphs of MoO<sub>3</sub>. After a synthesis process, these techniques let us to identify the presence of the h-MoO<sub>3</sub> phase in a rapid way. Studies have also been performed by electron microscopy (SEM and TEM) for the h-MoO<sub>3</sub> [8,11]; as well as XPS, magic-angle-spinning 1H- and 15N NMR spectroscopy studies [5,12]. Each characterization technique gives information about the size, morphology,


composition, crystalline structure of the rods.

The h-MoO<sub>3</sub> phase has been subjected to studies of structural stability under thermal or pressure treatments. Thermal studies of the hexagonal phase of MoO<sub>3</sub> have been reported by various research groups [2,5,8,10,11]. Differential Thermal Analysis (DTA), has been used to determine the h-MoO<sub>3</sub> to α-MoO<sub>3</sub> phase transformation temperature. Another important aspect related to stability, has been studied recently by C. C. Zhang et al, they investigated the stability of the h-MoO<sub>3</sub> phase under pressure, using a diamond anvil cell up to 28.7 GPa at room temperature [9]. They found that a transformation from h-MoO<sub>3</sub> to amorphous MoO<sub>3</sub> is obtained at pressures starting at 5.6 GPa. Optical studies of the h-MoO<sub>3</sub> phase have been done to determine the optical band gap of this material, according to the literature the optical band gap is in the order of 2.99 eV [4], 2.92-3.05 eV[8].


The aim of this work is to present a novel method to prepare well-formed, defect free h-MoO<sub>3</sub> rods. A detailed

**Table 1.** Comparison of dimensions of h-MoO<sub>3</sub> roads.


	Hans-Joachim et al.[1]	Pan et al.	Atuchin et al. [2]	Our work
Diameter	2.5 μm	1 μm	0.5 μm	0.5 μm -2.5 μm
Length	7.5 μm	10 μm	20 μm	12.6 μm

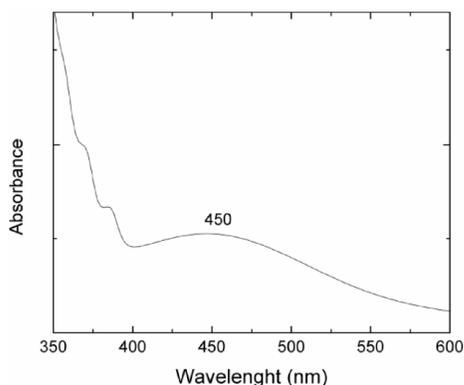

**Figure 1.** Absorbance spectrum of the sample at the time that started the heating treatment.

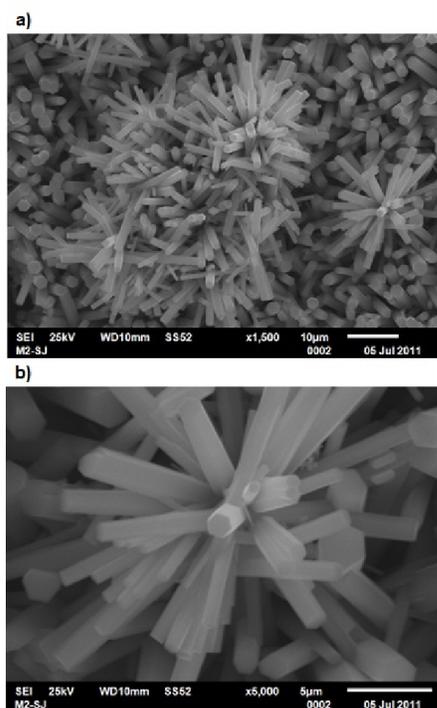

**Figure 2.** Images from SEM of h-MoO<sub>3</sub> rods.

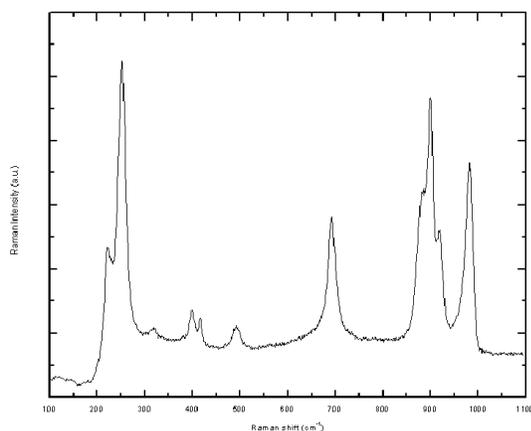

**Figure 3.** Raman Spectrum of h-MoO<sub>3</sub> rods.

characterization of the as obtained material includes Scanning Electron Microscopy (SEM) and microRaman spectroscopy.

## 2. Experimental

### 2.1 Preparation

A molybdenum (sheet) piece of 0.1g was immersed into a previously prepared mixture of 60% HCL and 40% HNO<sub>3</sub> (total volume utilized was 1 ml). After a given immersion time, the molybdenum piece was totally dissolved and the solution acquires orange-brown coloration. Molybdenum reacts with the mixture of acids to give water, nitric dioxide and complex ions  $MoCl_4^-$ . Figure 1 shows the absorption spectrum of the as-obtained solution, it was obtained with a Cary 5000 UV-Vis-NIR spectrophotometer, in the range of 350-600nm. It can observe absorption bands centered at 370, 380 and 450 nm. This last band is related with the color of the solution (orange-brown). The bands at 370 and 380 nm are related to the absorption of nitric dioxide formed after the reaction process of nitric acid and molybdenum.

In order to obtain molybdenum oxide, the resultant solution was treated thermally in a furnace in air. To this purpose, a cylindrical glass (0.5 cm in diameter and 3.2 cm tall) was placed inside the furnace. The molybdenum solution was heated up to 100 °C for 45 minutes. At the end of this period of time 0.25 g of powder was obtained.

### 2. 2. Characterization

The as-obtained sample was characterized by microRaman spectroscopy to study the nature of the synthesized material. A micro-Raman system (LabRaman HR-800 of Jobin-Yvon-Horiba), which uses a He-Ne laser ( $\lambda=632.8$  nm) as excitation source, was utilized in our study. A 100X microscope objective lens of an Olympus BX-41 optical microscope was used to focus the laser beam on the sample and to collect the scattered light. As per the morphological features of the obtained material, a scanning electron microscope (Jeol JSM6510 LV) was used to collect detailed images of the obtained structures. The as-obtained samples were set on graphite tape and the images were obtained through secondary electrons.

## 3. Results and discussion

Figure 2 shows the SEM micrographs for the powder obtained when the solution was thermally treated at 100 °C for 45 min. A large amount of straight hexagonal rods are very well formed, as it can be seen in micrograph 2(a). It is worth noting that the typical lamellar form of  $\alpha$ -MoO<sub>3</sub> is not observed in the SEM images. The material formed in a homogeneous way, such that all the grown rods possess hexagonal geometry. Notice too how some rods are linked forming hierarchical structures. In micrograph 2(b) we can see the excellent faceted surface quality being very smooth

**Table 2.** Raman frequencies reported for the h-MoO<sub>3</sub> crystalline phase.

Hans-Joachim et al.[1] (cm <sup>-1</sup> )	Pan et al. [4] (cm <sup>-1</sup> )	Atuchin et al. [2] (cm <sup>-1</sup> )	Silveira et al.[3] (cm <sup>-1</sup> )	Our work 632.8 (cm <sup>-1</sup> )
973	980	978	982	985
	916	912	923	922
900	901	901	903	901
	887	880	885	884
690	690	691	695	694
492	489	492	493	494
414	412		415	417
396	395	398	397	401
316	312	319	318	318
253	250	250	249	254
222	217	219	220	222
180	173	176	171	
148	134	134		
		121		

in each hexagonal rod. In table 1 we compare our obtained results to those of the hexagonal rods obtained by other research groups. It is clear that micro or submicro sized rods in diameters can be obtained by the synthesis methods reported in the literature.

The Raman spectrum of the hexagonal MoO<sub>3</sub> has been reported in the literature within the range 100-1000 cm<sup>-1</sup>. Table 2 summarizes the Raman frequencies for h-MoO<sub>3</sub> reported by several research groups. Figure 3 shows the microRaman spectrum of the h-MoO<sub>3</sub> rods that we obtained for the range 200-1100 cm<sup>-1</sup>. The Raman frequencies for h-MoO<sub>3</sub> obtained in our work are in good agreement with those reported by Silveira et al. (see table 2). This result complements our SEM evidence and it confirms that the powder synthesized by this rather simple method, is constituted by hexagonal molybdenum oxide rods crystallized in the h-MoO<sub>3</sub> phase. It is worth noting that the Raman frequencies of h-MoO<sub>3</sub> depend on its composition.

#### 4. Conclusions

The method of synthesis presented in this work is both simple and effective to prepare high quality hexagonal MoO<sub>3</sub> rods. The method is capable of producing micro-sized defect free hexagonal rods. A more detailed study is required to determine the formation mechanism, out of the acid mixture and dissolved molybdenum, which that makes it possible to grow straight hexagonal rods. In view of other known synthesis methods to obtain h-MoO<sub>3</sub>, ours is considerable simpler.

#### Acknowledgements

We acknowledge to Dr. Dora Solis-Casados for the Scanning Electron Microscopy images.

#### References

- [1]. Jimei Song, Xiong Wang, Xiaomin Ni, Huagui Zheng, Zude Zhang, Mingrong Ji, Tao Shen, Xingwei Wang, *Materials Research Bulletin* **40**, 1751 (2005).
- [2]. Jimei Song, Xiaomin Ni, Lisheng Gao, Huagui Zheng, *Materials Chemistry and Physics* **102**, 245 (2007).
- [3]. Jimei Song, Xiaomin Ni, Dongen Zhang, Huagui Zheng, *Solid State Sciences* **8**, 1164 (2006).
- [4]. Angamuthuraj Chithambararaj and Arumugam Chandra Bose, *Beilstein J. Nanotechnol.* **2**, 585 (2011).
- [5]. Hans-Joachim Lunk, Hans Hartl Monika A. Hartl, Martin J. G. Fait, Ilya G. Shenderovich, Michael Feist, Timothy A. Frisk, Luke L. Daemen, Daniel Mauder, Reinhard Eckelt, Andrey A. Gurinov, *Inorg. Chem.* **49**, 9400 (2010).
- [6]. V. V. Atuchin, T. A. Gavrilova, V. G. Kostrovsky, L. D. Pokrovsky, and I. B. Troitskaia, *Inorganic Materials* **44**, 622 (2008).
- [7]. Jose V. Silveira, Jerias A. Batista, Gilberto D. Saraiva, Josue Mendes Filho, Antonio G. Souza Filho, Shi Hue, Xun Wang, *Vibrational Spectroscopy* **54**, 179 (2010).
- [8]. Wenzhi Pan, Ruiyuan Tian, Hao Jin, Yanjun Guo, Liping Zhang, Xiaochun Wu, Lina Zhang, Zhihua Han, Guangyao Liu, Jianbo Li, Guanghui Rao, Hanfu Wang and Weiguo Chu, *Chem. Mater* **22**, 6202 (2010).
- [9]. C. C. Zhang, L. Zheng, Z. M. Zhang, R. C. Dai, Z. P. Wang, J. W. Zhang, and Z. J. Ding, *Phys. Status Solidi B* **248**, 1119 (2011).
- [10]. Zhuangzhi Wu, Dezhi Wang, Xun Liang, Aokui Sun, *Ultrasonics Sonochemistry* **18**, 288 (2011).
- [11]. S. R. Dhage, M.S. Hassan, O.-Bong Yang, *Materials Chemistry and Physics* **114**, 511 (2009).
- [12]. Shigehito Deki, Alexis Bienvenu Beleke, Yuki Kotani, Minoru Mizuhata, *Journal of Solid State Chemistry* **182**, 2362 (2009).
- [13]. A. Chithambararaj, A. Chandra Bose, *Journal of Alloys and Compounds* **509**, 8105 (2011).